

## RHEOLOGICAL AND MECHANICAL BEHAVIOR STUDY OF ECO-FRIENDLY CEMENT MORTAR MADE WITH MARBLE POWDER

Kahina Chahour

Civil Engineering Department, Mouloud Mammerie University of Tizi Ouzou, ALGERIA

Hamza Mechakra and Brahim Safi\*

Process Engineering Department/Faculty of Technology, University M'hamed Bougara of Bumerdes,  
ALGERIA

Nacera-Melissa Dehbi and Cylia Chaibet

Civil Engineering Department, Mouloud Mammerie University of Tizi Ouzou, ALGERIA

The work aim is to investigate the rheological and mechanical behavior of an eco-friendly mortar made with marble powder. Marble is have used as sand (total substitution of natural sand) and as an additional material (partial substitution of cement). Firstly, rheological tests were carried out on the cement pastes in order to study the effect of cement substitution by marble powder on the rheological behavior. Secondly, our study is devoted to evaluate the mechanical performances (flexural strength, compressive strength, mechanical behavior and ultrasonic pulse velocity) of a fluid mortar such as the case of the self-compacting mortars elaborated with the marble powder as an addition a material and as sand. The mechanical test results show that compressive strength and mechanical behavior of an ecological cement mortar made with marble waste as natural sand improved significantly. However, marble-based mortars with 100% of marble sand have given a mechanical strength similar to that obtained by control cement mortar (100% natural sand). It was also noted that it an ecological cement mortar made with 30% of marble powder as an addition a supplementary material can be obtained. This leads to a reduction in cement consumption and a reduction in CO<sub>2</sub> gas emissions caused by cement production.

**Key words:** powder marble wastes, mortar, sand, rheological properties, viscosity, mechanical strength, mechanical behavior and strength gain.

### 1. Introduction

Marble is a commonly utilized building material in the field of civil engineering, and its processing results in a substantial volume of waste generated in quarries and processing facilities. Over 30% of marble is typically discarded as waste in the form of powder or fine aggregates. Numerous studies have demonstrated the potential for reusing this type of waste in various applications, particularly in the construction materials sector. Extensive research has been conducted on incorporating marble waste into concrete formulations. Multiple investigations have explored the feasibility of utilizing marble dust waste as a mineral additive in concrete [1-9]. These studies generally found that marble dust had no adverse effects on the workability of fresh concrete but did have a detrimental impact on the mechanical properties of hardened concrete. Researchers have also examined the use of waste marble as an alternative to fine aggregates or as an additional material [10-17]. Binici and colleagues delved into the durability of concrete containing granite and marble as coarse aggregates [18, 19], demonstrating that substituting marble, granite, and ground blast furnace slag could lead to more durable concrete. Other research has investigated the properties of concretes and mortars incorporating marble powder waste. The results revealed that substituting 10% of natural sand with marble powder yielded the highest strength. Additionally, Gameiro *et al.* explored the characteristics of concretes

---

\* To whom correspondence should be addressed

created with marble waste by substituting aggregates at rates of 0%, 20%, 50%, and 100%, reporting that concrete incorporating marble aggregates exhibited superior properties compared to those with fine aggregates. More recently, Singh *et al.* [21, 22] provided an overview of research focused on partially replacing cement and sand with marble waste in concrete.

Regarding the use of marble waste in self-compacting concretes, studies evaluated the use 30% of waste marble as fines in concrete formulation. Results have shown that the fresh and hardened characteristics of concrete were improved. Hameed *et al.* [23] have evaluated the physical and mechanical characteristics of concrete by using the marble powder. With 15% of marble powder self-compacting concretes can be obtained having best characteristics, namely: the water absorption and permeability as well as fast chloride penetration and compressive strength. The utilization of limestone and marble powder in the concretes production was also studied [24]. These authors' findings revealed that marble powder improved the compressive strength at a rate that should not be underestimated. They reported that the highest compressive strength was observed in mixes that contained 10% marble [24, 25]. However, it should be noted that other researchers have found that using marble powder (especially sand substitution) leads to improvements in the mechanical characteristics of the concrete [3, 26]. Munir *et al.* [27] studied the characteristics of concrete elaborated with cement replacement by waste marble powder up to 40%. Singh *et al.* [22, 28] have reported that up to 15% or 20% of powder marble can be used (as cement substitution) in concrete production.

In this regard, our study aims to reclaim waste marble for reuse as sand in the formulation of fluid concrete. The experimental investigation was conducted in two phases. Initially, it involved the examination of the effect of cement substitution with marble powder (0%, 10%, 20%, 30% and 50% wt.) on the rheological behavior of the studied cement pastes, the other phase is devoted to evaluation of the mechanical performances (flexural strength, compressive strength, mechanical behavior and ultrasonic pulse velocity) of self-compacting mortars elaborated with the marble powder as cementitious materials (0%, 10%, 20%, 30% and 50% wt. of cement) and as sand (0%, 30%, 50%, 70% and 100% wt. of natural sand).

## 2. Experimental program

### 2.1. Raw materials

Portland cement, limestone filler, polycarboxylate-based superplasticizer, natural sand (0/3mm), marble powder (PM), are used as raw materials in this study. Portland cement is the CEM II 42.5 usually used in construction. The marble powder used is recovered from crushed wastes of the white marble quarry. River sand was used in mortar formulation, after being sieved to remove coarse grains, then washed and dried in an oven at 105°C for 24h. The chemical composition of the binder (cement and marble) is given in Tab.1. Physical characteristics of sand and marble is given in Tab.2. They are in accordance with the european standard EN 12620. Finally, to ensure the fluidity required for self-compacting mortars, a super-plasticizer conforming to EN-934-2 was used (see in Tab.2, which shows the physical properties of the superplasticizer applied).

Table 1. Chemical composition of binder (cement and marble powder).

chemical compound	portland cement (PC) [%]	marble powder (PM) [%]
CaCO <sub>3</sub>	-	99.05
CaO	63.02	55.06
P.C	-	45.26
MgO	1.87	1.01
SiO <sub>2</sub>	20.7	0.15
Al <sub>2</sub> O <sub>3</sub>	4.75	0.08
Fe <sub>2</sub> O <sub>3</sub>	3.75	0.07
SO <sub>3</sub>	1.98	-
Na <sub>2</sub> O	0.90	-

Table 2. Physical characteristics of natural sand, marble powder and superplasticizer.

properties	natural sand	marble powder	superplasticizer
true density	2.750	2.73	$1.06 \pm 0.01$
apparent density	2.66	2.63	
sand equivalent (%)	85	77	
fineness modulus	2.8	2.2	
porosity	2.18	3.72	
compactness	97.80	96.25	
absorption (by weight) (%)	0.71	0.41	
saturation (%)	0.75	0.87	
pH	-	-	4.5 – 6.5
content of Na <sub>2</sub> O eq	-	-	≤ 1 %
content of Cl <sup>-</sup>	-	-	≤ 0.1 %
dry extract	-	-	$28.01 \pm 2 %$

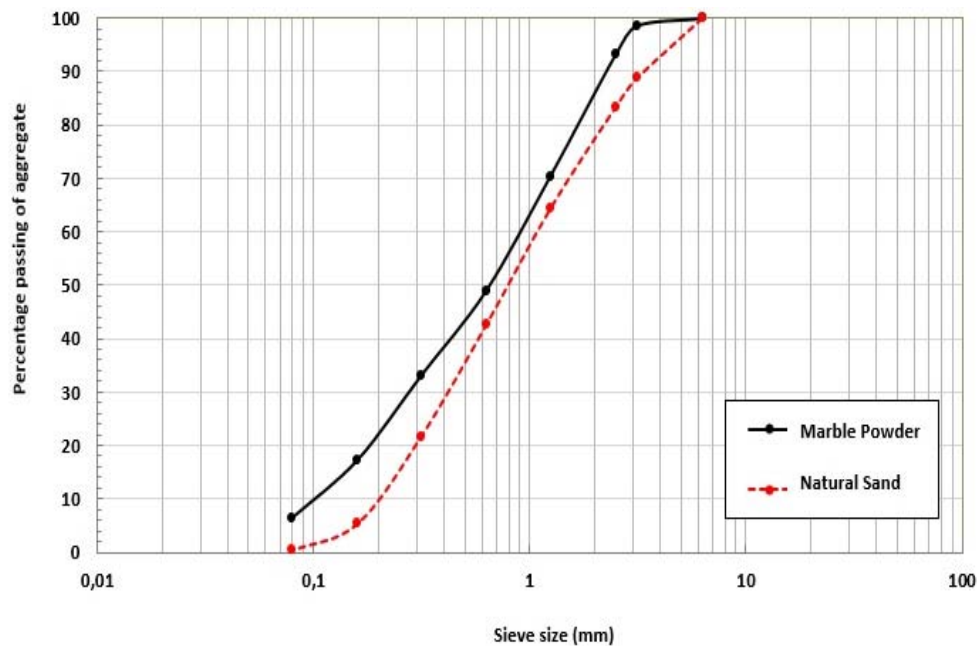


Fig.1. Particle-size distribution of the natural sand and marble powder

According to grain size distribution, the fineness modulus values of sand and marble powder are acceptable for a mortar, and natural sand can improve the mortar workability. Marble can be used to obtain a good workability and strength without segregation risks.

## 2.2. Mix design

The experimental study was conducted in two parts. First, the work involves studying the substitution effect of portland cement with marble powder (PM), the rheological behavior of cement pastes with fixed superplasticizer dosage and fixed water/binder ratio ( $W/B=0.35$ ). Table 4 gives mix design of the reference

cementitious paste (without marble powder). The other pastes were formulated by substituting cement with marble powder at (0%, 10%, 20%, 30% and 50% wt.). For the second phase of our study, fluid mortars, namely: self-compacting mortars (SCM), were elaborated according to the formulation given in Tab.5. The dosages of each mortar component have been obtained using the concrete-equivalent mortar design method [29-30]. By replacing the sand with marble at various dosages (30%, 50%, 70% and 100% by weight of natural sand), the other mortar variants are obtained.

Table 4. Reference cementitious paste used for rheological studies.

compounds	cement paste
cement* [g]	100
limestone fillers [g]	10
water [g]	38
superplasticizer [%]	1.3
W/B	0.35

\*Cement is substituted by marble powder ratio at 10%, 20%, 30% and 50% wt.

Table 5. Details of mortar mixes  $[kg / m^3]$

		water	limestone fillers	cement	powder marble	naturel sand
cement substitution	<b>MC0</b>	256	66	662	0	1373
	<b>MC10</b>	256	66	600	66.2	1373
	<b>MC20</b>	256	66	529.6	132.4	1373
	<b>MC30</b>	256	66	463.4	198.6	1373
	<b>MC50</b>	256	66	331	331	1373
sand substitution	<b>MS0</b>	256	66	662	0	1373
	<b>MS30</b>	256	66	662	412	961
	<b>MS50</b>	256	66	662	686.5	686.5
	<b>MS70</b>	256	66	662	961	412
	<b>MS100</b>	256	66	662	1373	0

### 2.3. Test methods

#### a) Rheological study

All rheological tests were made by using an AR2000 rheometer from TA Instruments (Figs 2 and 3). All rheological tests were performed according to a chosen protocol which is applied on series of cement pastes samples (Fig.2). Rheological study was performed according to an adequate protocol previously used for the cement pastes by the authors [29]. It is necessary to pre-shear at  $350 S^{-1}$  for 60 seconds to homogenize the pastes and to obtain reproducible rheological measurements (laboratory conditions  $T = 20 \pm 1^\circ C$ ). The measurement was carried out under the imposed shear rate of  $600 S^{-1}$ .

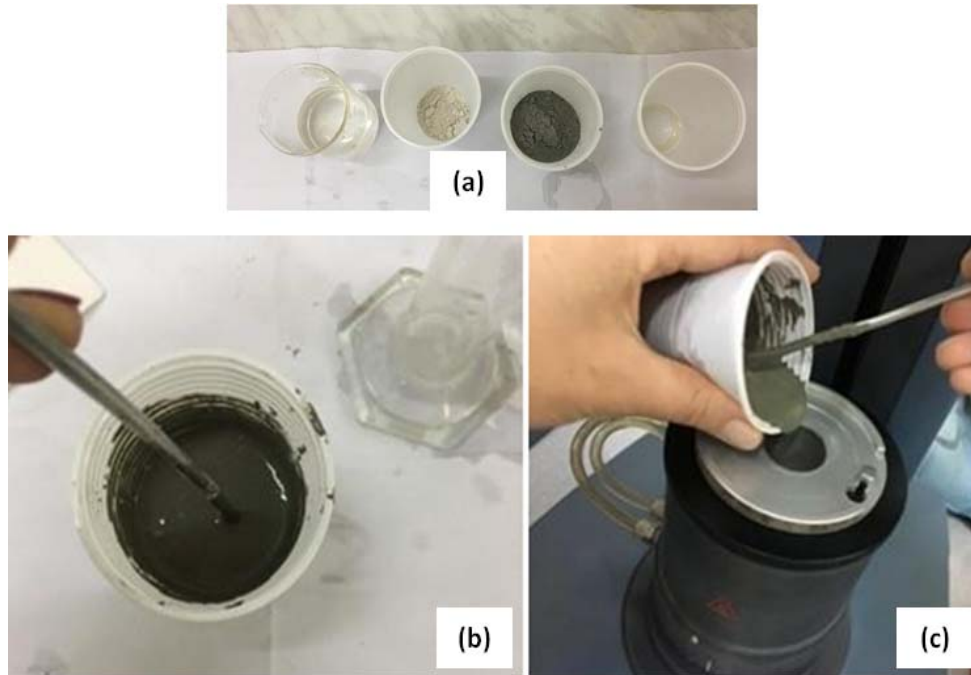


Fig.2. Preparing of cement pastes: (a) raw materials (b) mixing of cement pastes (c) preparing of rheological tests.

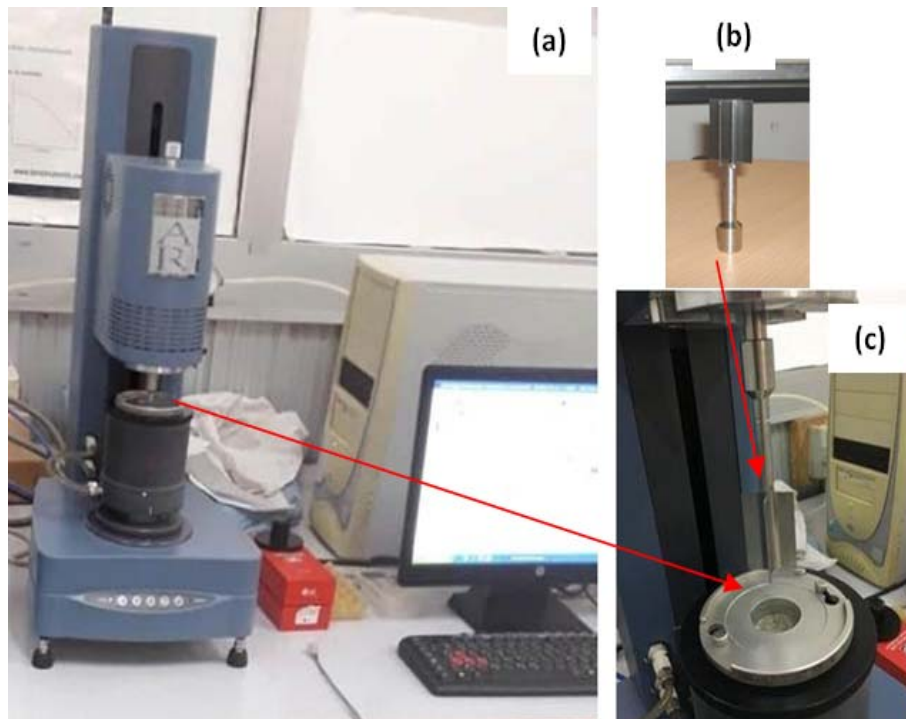


Fig.3. Rheological equipment: (a) AR2000 rheometer, (b) rotor valve geometry used, (c) cement paste sample.

### b) Fresh properties

The fluidity of prepared mortar was measured after each preparation using the mini-cone slump test, by measuring the flow diameter of the mortar after slump test according to RFNARC [31].

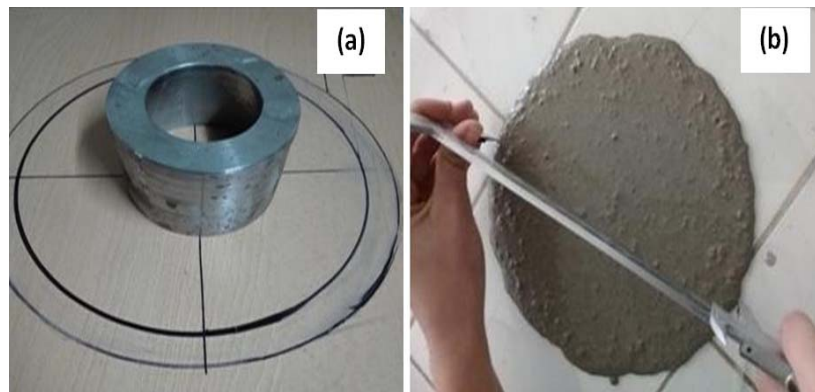


Fig.4. Slump test: (a) mini-cone (b) fluidity of mortar.

### c) Mechanical properties

Prismatic specimens  $40 \times 40 \times 160 \text{ mm}^3$  and cubic specimens  $50 \times 50 \times 50 \text{ mm}^3$  were produced for each mortar mixture in order to assess their mechanical properties in the hardened state. These assessments were conducted using a strength testing machine. At various time intervals during storage in water at a controlled temperature of  $21 \pm 1^\circ\text{C}$ , the specimens were subjected to tests to determine their bending strength, uniaxial compression strength, and mechanical behavior (as depicted in Fig.5a and 5b). The cubic specimens were specifically utilized to assess the compressive strength and mechanical behavior, while the prismatic samples were employed for evaluating flexural strength and conducting ultrasonic tests (as indicated in Fig.5c). Three-point bending and uniaxial compression tests were performed at 2, 7, and 28 days on the specimens stored in water, following the guidelines outlined in ASTM C348 and ASTM C349 [32-33]. To evaluate the mechanical behavior of the mortars, cubic samples  $50 \times 50 \times 50 \text{ mm}^3$  were subjected to a uniaxial compression test.



Fig.5. Mechanical testing: (a) flexural tests, (b) compressive and behavior mechanical, (c) cubic and prismatic specimens.





Fig.6. Ultrasonic pulse velocity tests carried out on prismatic samples.

### 3. Results and discussions

#### 3.1. Rheological properties of studied cement pastes

Figures 7 and 8 give the variations in shear stress ( $\tau_p$ ) and plastic viscosity ( $\eta_p$ ) of cement pastes at different levels of marble powder (PM) substitution, as a function of shear rate. It is evident that both shear stress and plastic viscosity increase as the level of cement substitution with marble powder (PM) rises, up to a 20% substitution rate. Beyond this point, a decrease of these parameters is observed at a 30% substitution level of cement with marble powder. This trend can be attributed to the specific surface characteristics of marble powder particles, which increase the demand for water to facilitate surface wetting. Beyond the 30% substitution mark, marble powder contributes to enhanced fluidity by reducing the viscosity of the cement paste [29, 34, 35], as demonstrated in the figure. Notably, the cementitious pastes exhibit greater fluidity and improved flow characteristics at substitution rates of 30% and 50% compared to those at 10% and 20%. Several studies have previously reported the influence of specific surface area on rheological parameters [30, 34-36].

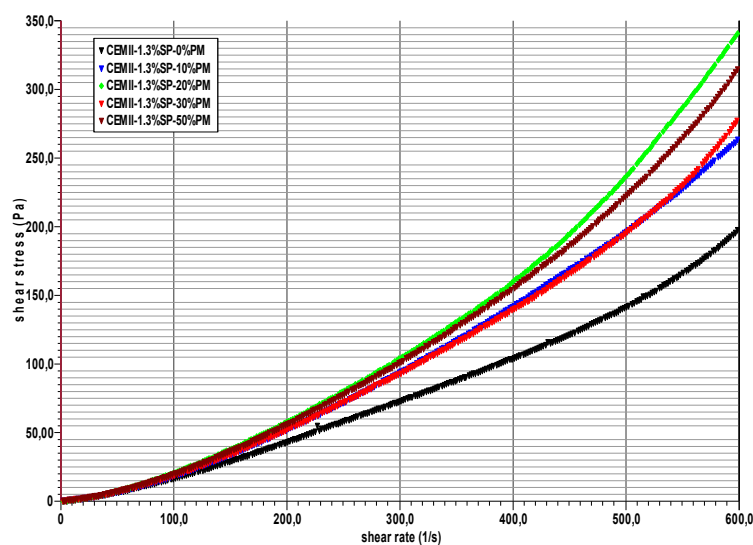


Fig.7. Share stress as a function of share rate: at different cement substitution rate by marble powder.

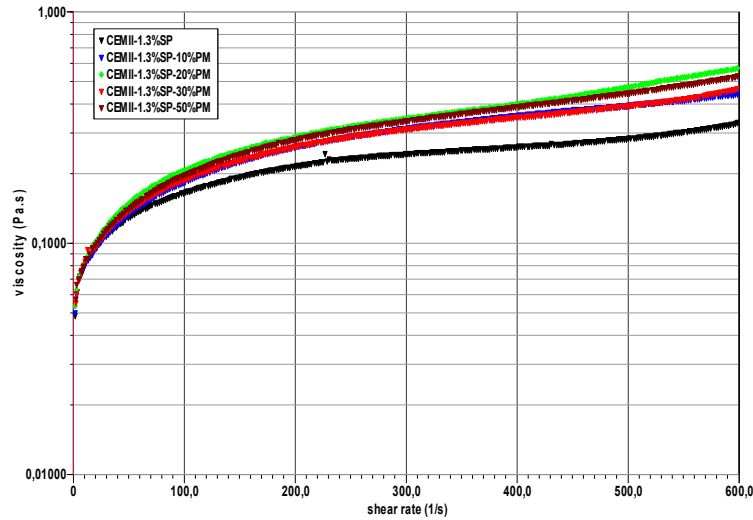


Fig.8. Plastic viscosity as a function of share rate: at different cement substitution rate by marble powder.

To study the rheological behavior of the cement pastes studied, the rheometry software TA Data Analysis of the AR2000 rheometer enabled us to identify the rheological behavior of all the cementitious pastes studied (see Fig.9). Indeed, by calibrating the models already existing in the software, the rheological behavior of these pastes could be identified. According to the results obtained, all studied cement pastes have a behavior of a plastic Bingham fluid identical to that of the Herschel-Buckley rheological model described by the Eq.(3.1), which is consistent with what exists in the literature [29, 35-37].

$$\tau_p = \tau_0 + K\dot{\gamma}^n, \quad (3.1)$$

$\tau_p$  : is shear stress;  $\tau_0$  : is yield stress;  $\dot{\gamma}$  : is shear rate;  $K$ : is the consistency index;  $n$ : is the flow index.

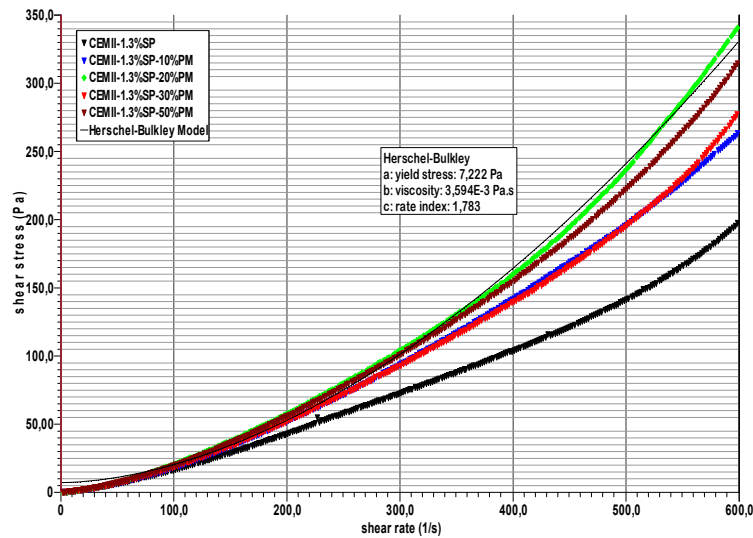


Fig.9. Rheological behavior of cement pastes studied.



### 3.2. Fresh and hardened properties of mortars studied

#### a). Fluidity of mortars

The variation in mortar fluidity for both cases of marble powder substitution, namely cement and sand, is graphically represented in Fig.10.

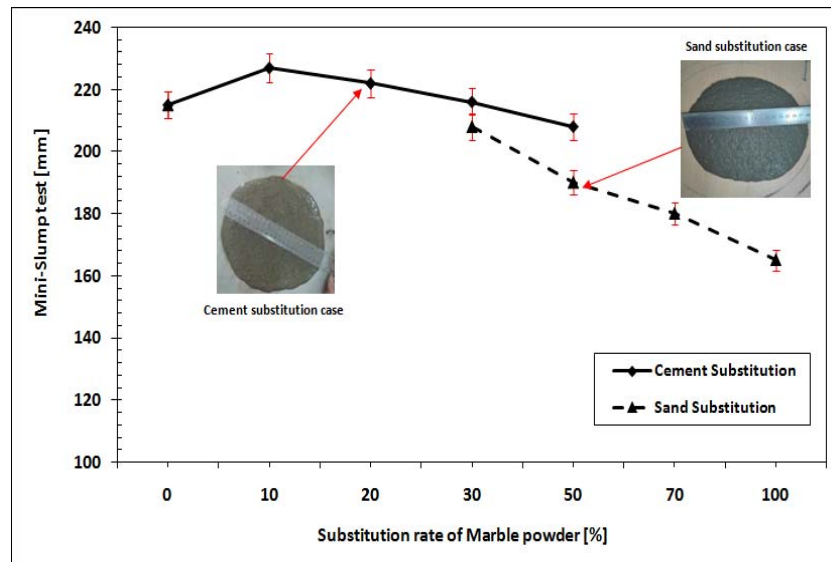


Fig.10. Fluidity of mortars based on marble powder (cement and sand substitution).

Regarding the substitution of cement with marble powder, it is worth highlighting that there is an increase in fluidity observed in the MC10 mortar, followed by the MC20 mortar. Additionally, it is evident that the fluidity of the mortar diminishes as the rate of substitution with marble powder increases. In fact, up to a 50% substitution rate, the reduction in the cake's diameter obtained is not particularly significant. Furthermore, the mortar meets the criteria for self-compacting concretes in terms of both fluidity and ease of handling. Baboo *et al.* [38] noted a slight improvement in concrete workability when replacing cement with marble powder up to 20%. However, other authors have reported that while flow ability decreases, it still falls within the medium range as per IS specifications. Many researchers have also observed that the most substantial enhancement in fluidity occurs up to a 10% marble powder substitution [39-40].

However, for the case of sand substitution with marble powder, the results show that the fluidity of the mortars has increased for mortars at 30% sand substitution, compared to the control mortar. As soon as this threshold is exceeded, a decrease in the mortar fluidity is noted with the increase of the sand substitution rate. Certainly, up to a 50% substitution, the reduction is not significant, and the mortar satisfies the criteria for self-compacting mortars regarding fluidity and ease of application. This can be explained by the effect of specific surface of powder marble on mortar fluidity which has been reported by several authors [37-39]. Once the sand substitution with marble powder exceeds 70%, the self-compacting mortars experience a slight reduction in their fluidity, although they still fall within the self-compacting mortar classification. It is worth mentioning that this decrease in fluidity can be compensated for by increasing the superplasticizer dosage.

#### b) Compressive and flexural strength

Figure 11a reveals that the compressive strength rises with increasing curing time across all the self-compacting mortars. Notably, it was observed that the strength of mortars remains consistent for M0 and MC10 compositions. However, when the marble powder content reaches 20% in MC20, a slight decline in the

compressive strength becomes apparent. The strength for MC30 and MC50 mortars decreases compared to the control mortar, regardless of the curing age of mortars. It should also be noted that the highest value of the compressive strength recorded at 28 days is around  $74 \text{ MPa}$  for the control mortar, followed by the MC10 mortar at  $66 \text{ MPa}$ .

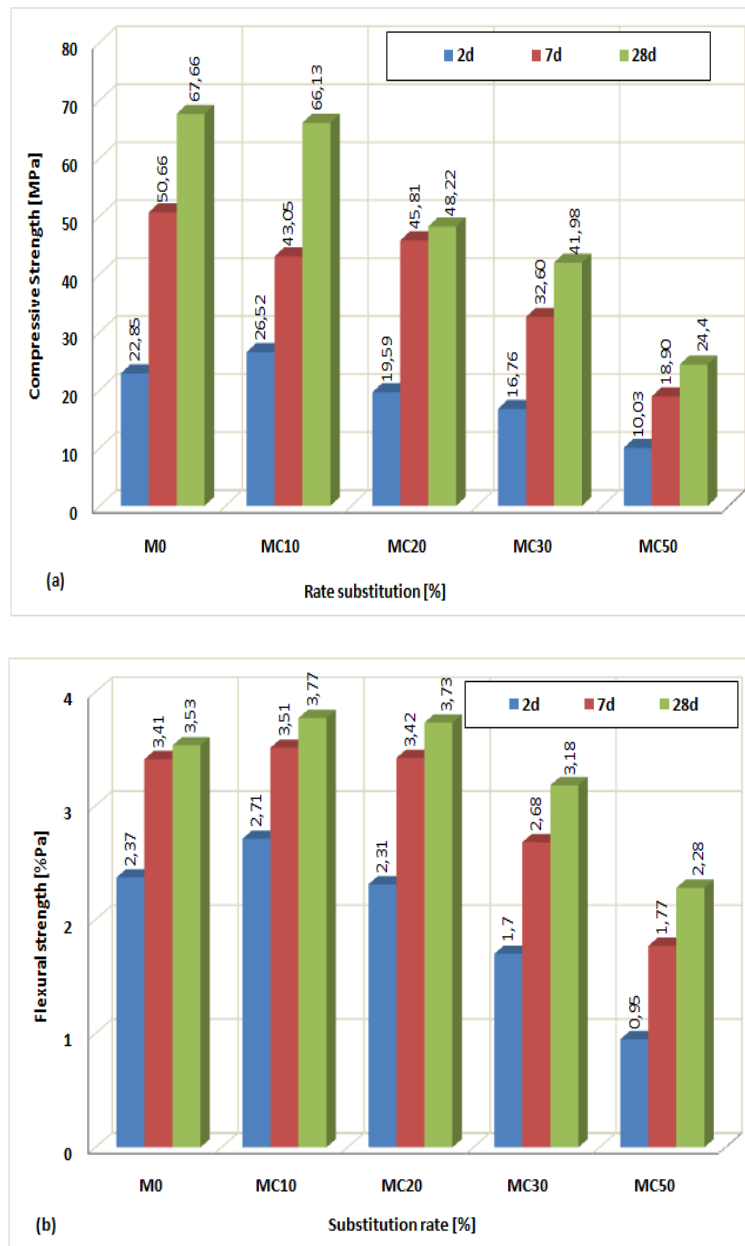


Fig.11. Mechanical strength development of studied self-compacting mortars based on marble powder: (a) compressive, (b) flexural; cement substitution case.

For other mortar mixtures, strength values remain in the category of self-compacting mortars, except for the MC50 mortar where the recorded strength is  $24 \text{ MPa}$ , that this value is suitable for construction. It has been reported that up to  $10\%$  marble powder used as cement, can give a better mortar in terms of fluidity and compressive strength. The substitution level of cement with marble powder can be further extended up to  $20\%$ ,

as 28-day compressive strength of MC20 mortar was a good value of strength with 48 MPa. The same observation with a level of 20% replacement of cement by marble powder was made in [17, 40-41].

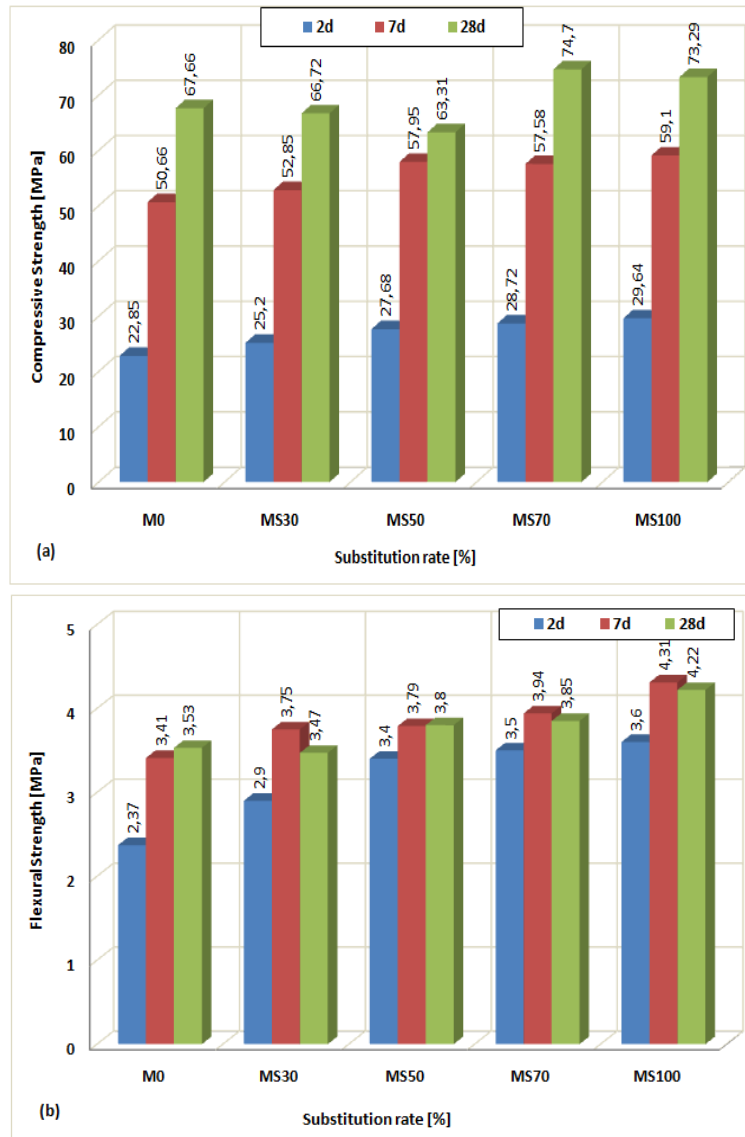


Fig.12. Mechanical strength development of studied self-compacting mortars based on marble powder: (a) compressive, (b) flexural; sand substitution case.

Furthermore, it is noteworthy that the flexural strength exhibited improvements in both MC10 and MC20 mortars when compared to the control mortar, as depicted in Fig.11b. However, after reaching a 20% substitution level of cement with marble powder, a reduction in flexural strength was observed. It was also observed that up to a 30% cement substitution with marble powder, the flexural strength of the mortar remained satisfactory and closely approached that achieved by the control mortar. The effect of marble powder as sand replacement on the compressive and flexural strength of studied self-compacting mortars is given in Figs 12a and 12b.

Previous research focused on incorporating marble powder as a fine aggregate in mortars or concretes has consistently demonstrated the highly advantageous impact of using marble powder in lieu of sand, particularly regarding mechanical performance and material durability [11, 12]. Our findings clearly

underscore the effectiveness of marble powder when employed as a sand replacement. Indeed, we observed a noticeable enhancement in both compressive and flexural strength across all curing periods when marble powder was used as a complete sand substitute, with a remarkable 10% improvement in compressive strength compared to the control mortar.

Furthermore, a self-compacting mortar formulated with total sand substitution by marble powder can achieve an impressive compressive strength of approximately 74 MPa at 28 days, alongside a flexural strength of approximately 4.22 MPa. In comparison with results obtained from existing literature [39-42], it can be concluded that this marble powder-based mortar demonstrate a significant potential as a sustainable alternative to traditional cement mortars in construction applications.

### 3.3. Mechanical behavior of studied mortars

The mechanical characteristics of each mortar mixture were determined through experimental analysis, as illustrated by the stress-strain curve in Fig.13.

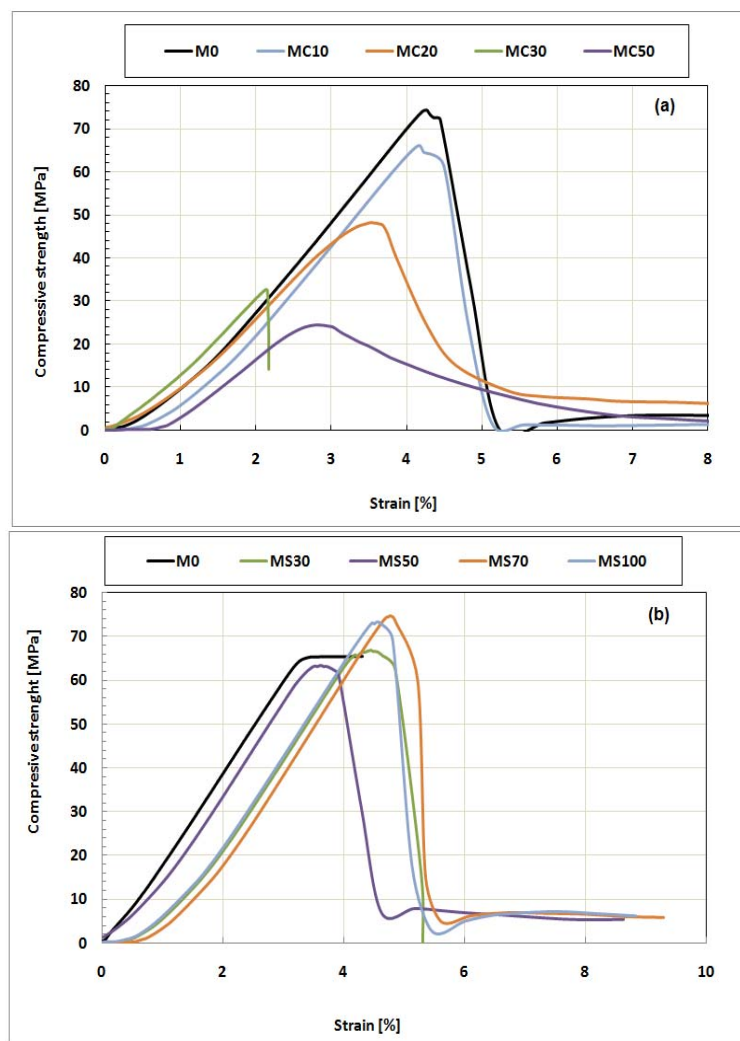


Fig.13. Stress-strain behavior of powder marble-based mortars at 28-day, (a) cement substitution, (b) sand substitution.

All the mortars under investigation exhibited a brittle behavior, characterized by an initial elastic range followed by rupture at a maximum load. However, it is worth noting that a mortar (MC10), featuring a 10% substitution of cement with marble powder, displayed identical mechanical behavior to the reference mortar MC0, as depicted in Fig.13a. On the other hand, as the cement substitution with marble powder increased up to 30%, the mortar's mechanical behavior continued to exhibit brittleness, albeit with a reduction in maximum load and less deformation when compared to the MC0 mortar, as shown in Fig.10a [43-46].

In the context of replacing natural sand with marble powder, the findings related to mechanical behavior are quite intriguing. In fact, when substituting sand with marble powder up to 70%, the mortar's mechanical behavior remains brittle and mirrors that of the control mortar, as evidenced in Fig.13b. A marginal enhancement in maximum load is noticeable, accompanied by reduced deformation compared to the control mortar, as reported in previous studies [42].

### 3.4. Ultrasonic testing of studied mortars

Ultrasonic pulse velocity (UPV) was analyzed across all mortar samples to assess mortar density and to gauge the influence of marble powder. Figure 14 showcases the sound velocity results in relation to the substitution of cement and sand with marble powder, along with curing time at 28 days. The results show a slight decrease in the sound velocity of the mortars beyond 30% substitution of cement with marble powder compared to the reference mortar specimens. However, it was noted that a clear improvement in mortar compactness is reflected by an increase in sound velocity when sand is fully substituted with marble powder. It should also be noted that the good adhesion of the marble grains with the cement paste favors well the compactness of the mortars (see Fig.14).

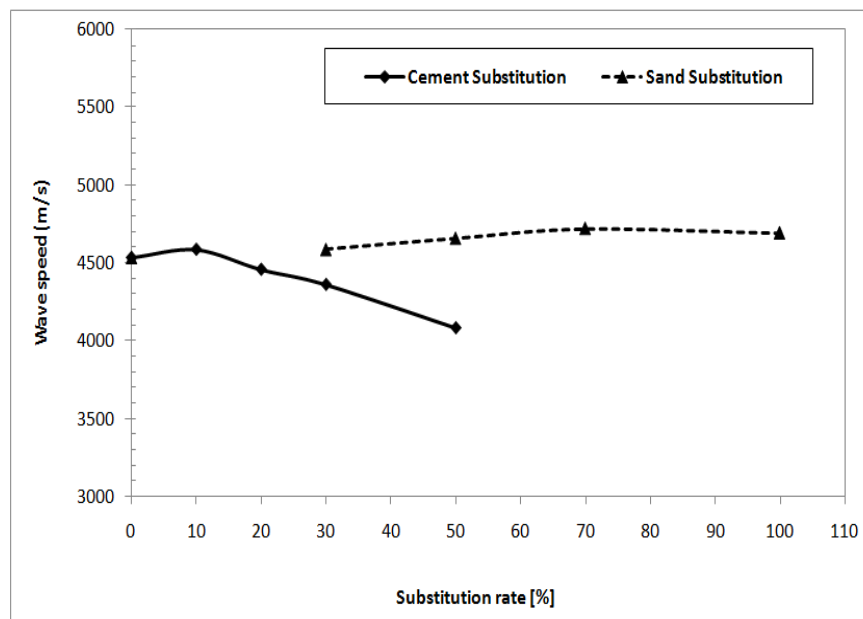


Fig.14. Ultrasonic pulse velocity evolution of powder marble-based mortars measured at 28-days.

## 4. Conclusion

The study focused on the use of marble powder as an additional material and a fine aggregate in the manufacturing of fluid mortar. The rheological and mechanical behavior of self-compacting mortars made

with powder marble (in two substitution cases: cement and natural sand) were reviewed and compared. it can be concluded that;

Beyond 30% of cement substitution, the marble powder has improved the fluidity by decreasing the shear stress and viscosity of the cement paste. The effect of the specific surface of powder marble on rheological parameters has been observed. Beyond 70% sand substitution with marble powder, the self-compacting mortars lose a little their fluidity, but they remain in the category of self-compacting mortars.

Up to 70% replacement of natural sand with marble powder, a self-compacting mortar with acceptable fresh characteristics can be obtained. Indeed, an improvement of compressive and flexural strength at all curing age was observed for all self-compacting mortars up to 100% sand substitution. However, a 20% reduction in cement consumption translates into fluid mortars with acceptable characteristics for construction.

At a 30% substitution rate of cement with marble powder, the mechanical performance of the mortar continues to display brittleness. Nevertheless, there is a noticeable decrease in the maximum load and reduced deformation compared to the control mortar. In the case of sand substitution with marble powder, the findings regarding mechanical behavior are particularly noteworthy. Remarkably, up to a 70% substitution rate of sand with marble powder, the mortar's mechanical behavior remains brittle and mirrors that of the control mortar.

## Acknowledgements

The contributions of the research team at the Materials, Process, and Environment Research Unit (URMPE) and the Laboratory of Rheology of Complex Fluids are sincerely appreciated by all the authors.

## Nomenclature

$PC$	– Portland cement
$PM$	– marble powder
$SCM$	– self-compacting mortar
$SCC$	– self-compacting concrete
$W/B$	– water/binder ratio
$MC$	– mortar with cement substitution
$MS$	– mortar with sand substitution
$\tau_p$	– shear stress
$\dot{\gamma}^n$	– shear rate
$\eta_p$	– plastic viscosity
$\tau_0$	– yield stress
$K$	– consistency index
$n$	– flow index

## References

- [1] Tunc E.T. (2019): *Recycling of marble waste: A review based on strength of concrete containing marble waste.*– Journal of Environmental Management, vol.231, 86-97, <https://doi.org/10.1016/j.jenvman.2018.10.034>
- [2] Alyamac K.E., Ghafari E. and Ince R. (2017): *Development of eco-efficient self-compacting concrete with waste marble powder using the response surface method.*– Journal of Cleaner Production, vol.144, pp.192-202, <https://doi.org/10.1016/j.jclepro.2016.12.156>
- [3] Aliabdo A.A., Abd Elmoaty M. and Auda E.M. (2014): *Re-use of waste marble dust in the production of cement and concrete.*– Construction and Building Materials, vol.50, pp.28-41, <https://dx.doi.org/10.1016/j.conbuildmat.2013.09.005>
- [4] André A., de Brito J., Rosa A. and Pedro D. (2014): *Durability performance of concrete incorporating coarse aggregates from marble industry waste.*– J. Clean. Prod., vol.65, 389-396. <https://doi.org/10.1016/j.jclepro.2013.09.037>

- [5] Arel H.S. (2016): *Recyclability of waste marble in concrete production.*– J. Clean. Prod., vol.131, pp.179-188, <https://doi.org/10.1016/j.jclepro.2016.05.052>
- [6] Aruntas H.Y., Gürü M., Dayı M. and Tekin I. (2010): *Utilization of waste marble dust as an additive in cement production.*– Materials & Design, vol.31, No.8, pp.4039-4042, <https://doi.org/10.1016/j.matdes.2010.03.036>
- [7] Ashish D.K. (2018): *Feasibility of waste marble powder in concrete as partial substitution of cement and sand amalgam for sustainable growth.*– J. Build. Eng., vol.15, pp.236-242, <https://doi.org/10.1016/j.jobe.2017.11.024>
- [8] Bacarji E., Toledo Filho R.D., Koenders E.A.B., Figueiredo E.P. and Lopes J.L.M.P. (2013): *Sustainability perspective of marble and granite residues as concrete fillers.*– Construct. Build. Mater., vol.45, pp.1-10, <https://doi.org/10.1016/j.conbuildmat.2013.03.032>
- [9] Selim F.A., Hashem F.S. and Amin M.S. (2020): *Mechanical, microstructural and acid resistance aspects of improved hardened Portland cement pastes incorporating marble dust and fine kaolinite sand.*– Construction and Building Materials, vol.251, pp.118992, <https://doi.org/10.1016/j.conbuildmat.2020.118992>
- [10] Ozkaya K., Ayırmis N. and Ozdemir S. (2015): *Potential use of waste marble powder as an adhesive filler in the manufacture of laminated veneer lumber.*– BioResources, vol.10, No.1, pp.1686-1695, <https://doi.org/10.15376/BIORES.10.1.1686-1695>
- [11] Bilgin N., Yeprem H.A., Arslan S., Bilgin A., Günay E. and Marşoglu M. (2012): *Use of waste marble powder in brick industry.*– Construct. Build. Mater., vol.29, pp.449-457, <https://doi.org/10.1016/j.conbuildmat.2011.10.011>
- [12] Buyuksagis I.S., Uygunoglu T. and Tatar E. (2017): *Investigation on the usage of waste marble powder in cement-based adhesive mortar.*– Construct. Build. Mater., vol.154, pp.734-742. <https://doi.org/10.1016/j.conbuildmat.2017.08.014>
- [13] Chandra S. and Choudhary R. (2012): *Performance characteristics of bituminous concrete with industrial wastes as filler.*– J. Mater. Civ. Eng., vol.25, No.11, pp.1666-1673, [https://doi.org/10.1061/\(ASCE\)MT](https://doi.org/10.1061/(ASCE)MT)
- [14] Ghani A., Ali Z., Khan F.A., Shah S.R., Khan S.W. and Rashid M. (2020): *Experimental study on the behavior of waste marble powder as partial replacement of sand in concrete.*– SN Applied Sciences, vol.2, pp.1-13, <https://doi.org/10.1007/s42452-020-03349-y>
- [15] Corinaldesi V., Moriconi G. and Naik T.R. (2010): *Characterization of marble powder for its use in mortar and concrete.*– Construct. Build. Mater., vol.24, No.1, pp.113-117, <https://doi.org/10.1016/j.conbuildmat.2009.08.013>
- [16] Çınar M.E. and Kar F. (2018): *Characterization of composite produced from waste PET and marble dust.*– Construct. Build. Mater., vol.163, pp.734-741, <https://doi.org/10.1016/j.conbuildmat.2017.12.155>
- [17] Olusunle S.O.O., Ezenwafor T.C., Jiddah-Kazeem B.S., Kareem A., Akinribide O.J. and Oyelami A.T. (2015): *Effect of organic waste on crystal structure and mechanical properties of concrete.*– Journal of Minerals and Materials Characterization and Engineering, vol.3, No.05, pp.427, <https://doi.org/10.4236/jmmce.2015.35045>
- [18] Binici H., Kaplan H. and Yilmaz S. (2007): *Influence of marble and limestone dusts as additives on some mechanical properties of concrete.*– Scientific Research and Essay, vol.2, No.9, pp.372-379 <https://hdl.handle.net/11499/18867>
- [19] Binici H., Shah T., Aksogan O. and Kaplan H. (2008): *Durability of concrete made with granite and marble as recycle aggregates.*– Journal of Materials Processing Technology, vol.208, No.1-3, pp.299-308, <https://doi.org/10.1016/j.jmatprotec.2007.12.120>
- [20] Gameiro F., de Brito J. and Correia da Silva D. (2014): *Durability performance of structural concrete containing fine aggregates from waste generated by marble quarrying industry.*– Eng. Struct., vol.59, pp.654-662, <https://doi.org/10.1016/j.engstruct.2013.11.026>
- [21] Singh M., Choudhary K., Srivastava A., Sangwan K.S. and Bhunia D. (2017a): *A study on environmental and economic impacts of using waste marble powder in concrete.*– J. Build. Eng. vol.13, pp.87-95, <https://doi.org/10.1016/j.jobe.2017.07.009>
- [22] Singh M., Srivastava A. and Bhunia D. (2017b): *An investigation on effect of partial replacement of cement by waste marble slurry.*– Construct. Build. Mater., vol.134, pp.471-488, <https://doi.org/10.1016/j.conbuildmat.2016.12.155>
- [23] Hameed M.S., Sekar A.S.S. and Saraswathy V. (2012): *Strength and permeability characteristics study of self-compacting concrete using crusher rock dust and marble sludge powder.*– Arabian Journal for Science and Engineering, vol.37, pp.561-574, <https://doi.org/10.1007/s13369-012-0201-x>
- [24] Gesoğlu M., Guneyisi E., Kocabağ M.E., Bayram V. and Mermerdaş K. (2012): *Fresh and hardened characteristics of self-compacting concretes made with combined use of marble powder, limestone filler, and fly ash.*– Construct. Build. Mater., vol.37, pp.160-170, <https://doi.org/10.1016/j.conbuildmat.2012.07.092>
- [25] Pathan V.G. and Pathan M.G. (2014): *Feasibility and need of use of waste marble powder in concrete production.*– IOSR Journal of Mechanical and Civil Engineering, vol.6, No.1, pp.23-26. ID: 55388264



- [26] Chahour K. and Safi B. (2020): *Mechanical behavior and chemical durability of marble-based mortar: Application to panels subjected to punching.*– Construction and Building Materials, vol.232, pp.117245, <http://dx.doi.org/10.1016/j.conbuildmat.2019.117245>
- [27] Munir M.J., Kazmi S.M.S. and Wu Y.F. (2017): *Efficiency of waste marble powder in controlling alkali-silica reaction of concrete: A sustainable approach.*– Construction and Building Materials, vol.154, pp.590-599, <https://doi.org/10.1016/j.conbuildmat.2017.08.002>
- [28] Khodabakhshian A., De Brito J., Ghalehnovi M. and Shamsabadi E.A. (2018): *Mechanical, environmental and economic performance of structural concrete containing silica fume and marble industry waste powder.*– Construct. Build. Mater., vol.169, pp.237-251, <https://doi.org/10.1016/j.conbuildmat.2018.02.192>
- [29] Safi B., Benmounah A. and Saidi M. (2011): *Rheology and zeta potential of cement pastes containing calcined silt and ground granulated blast-furnace slag.*– Materiales de Construcción, vol.61, No.303, pp.353-370, <https://doi.org/10.3989/mc.2011.61110>
- [30] Safi B., Aknouche H., Mechakra H., Aboutaleb D. and Bouali K. (2018): *Incorporation mode effect of nano-silica on the rheological and mechanical properties of cementitious pastes and cement mortars.*– In IOP Conference Series: Earth and Environmental Science, vol.143, No.1, pp.012015, IOP Publishing, DOI 10.1088/1755-1315/143/1/012015
- [31] EFNARC: *Specification and guidelines for self-compacting concrete.*– Feb. (2002), pp 29-35, Free pdf copy downloadable from <http://www.efnarc.org>
- [32] ASTM C348 - 08: *Standard Test Method for Flexural Strength of Hydraulic-Cement Mortars.*– which appears in the Annual Book of ASTM Standards, vol.04.01.
- [33] ASTM C349 - 08: *Standard Test Method for Compressive Strength of Hydraulic-Cement Mortars (Using Portions of Prisms Broken in Flexure).*– which appears in the Annual Book of ASTM Standards, vol.04.01.
- [34] Safi B., Saidi M., Daoui A., Bellal A., Mechekak A. and Toumi K. (2015): *The use of seashells as a fine aggregate (by sand substitution) in self-compacting mortar (SCM).*– Construction and Building Materials, vol.78, pp.430-438, <https://doi.org/10.1016/j.conbuildmat.2015.01.009>
- [35] Lecheb S., Chellil A., Chahour K. and Safi B. (2021): *Foamed glass granulated-based self-compacting mortars: open-porosity effect on rheological and mechanical properties.*– Cement-Wapno-Beton = Cement Lime Concrete, vol.26, No.3, pp.242-252, doi:10.32047/cwb.2021.26.3.6
- [36] Li H., Ji D., Chen C., Wang X., Tu J., Zhang K. and Ding A. (2021): *Effect of fatty acid methyl ester polyoxyethylene ether on the rheological properties of cement filled with artificial marble waste powders.*– Journal of Cleaner Production, vol.328, pp.129503, <https://doi.org/10.1016/j.jclepro.2021.129503>
- [37] Çınar M., Karpuzcu M. and Çanakçı H. (2019): *Effect of waste marble powder and fly ash on the rheological characteristics of cement based grout.*– Civil Engineering Journal, vol.5, No.4, pp.777-788, <http://dx.doi.org/10.28991/cej-2019-03091287>
- [38] Baboo R., Khan H.N., Kr A., Rushad S.T. and Duggal S.K. (2011), *Influence of marble powder/granules in concrete mix.*– Int. J. Civil Struct. Eng., vol.1, No.4, pp.827-834, doi:10.6088/ijcser.00202010070
- [39] Alyousef R., Benjeddou O., Soussi C., Khadimallah M.A. and Mustafa Mohamed A. (2019): *Effects of incorporation of marble powder obtained by recycling waste sludge and limestone powder on rheology, compressive strength, and durability of self-compacting concrete.*– Advances in Materials Science and Engineering, <https://doi.org/10.1155/2019/4609353>
- [40] Wang J., Ma B., Tan H., Du C., Chu Z., Luo Z. and Wang P. (2021): *Hydration and mechanical properties of cement-marble powder system incorporating triisopropanolamine.*– Construction and Building Materials, vol.266, pp.121068, <https://doi.org/10.1016/j.conbuildmat.2020.121068>
- [41] Saidi M., Ait-Medjber F., Safi B. and Samar M. (2014): *Recycling of aggregates from construction demolition wastes in concrete: Study of physical and mechanical properties.*– International Journal of Civil and Environmental Engineering, vol.8, No.12, pp.1307-1311, doi.org/10.5281/zenodo.1097437
- [42] Seghir N.T., Mellas M., Sadowski Ł. and Žak A. (2018): *Effects of marble powder on the properties of the air-cured blended cement paste.*– Journal of Cleaner Production, vol.183, pp.858-868, <https://doi.org/10.1016/j.jclepro.2018.01.267>
- [43] Ulubeyli G.C. and Artir R. (2015): *Properties of hardened concrete produced by waste marble powder.*– Procedia-Social and Behavioral Sciences, vol.195, pp.2181-2190, <https://doi.org/10.1016/j.sbspro.2015.06.294>
- [44] Oza R.B., Kangda M.Z., Agrawal M.R., Vakharia P.R. and Solanki D.M. (2022): *Marble dust as a binding material in concrete: A review.*– Materials Today: Proceedings, vol.60, pp.421-430, <https://doi.org/10.1016/j.matpr.2022.01.278>

- [45] Kuoribo E. and Mahmoud H. (2022): *Utilisation of waste marble dust in concrete production: a scientometric review and future research directions.*– Journal of Cleaner Production, pp.133872. <https://doi.org/10.1016/j.jclepro.2022.133872>
- [46] Silva D., Gameiro F. and de Brito J. (2014): *Mechanical properties of structural concrete containing fine aggregates from waste generated by the marble quarrying industry.*– Journal of Materials in Civil Engineering, vol.26, No.6, pp.04014008, [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0000948](https://doi.org/10.1061/(ASCE)MT.1943-5533.0000948)

Received: November 2, 2023

Revised: December 1, 2013